

# Electronic structures of $\text{Zn}_{1-x}\text{Co}_x\text{O}$ using photoemission and x-ray absorption spectroscopy

S. C. Wi, J.-S. Kang\*, J. H. Kim, S.-B. Cho, B. J. Kim, S. Yoon, and B. J. Suh  
*Department of Physics, The Catholic University of Korea, Puchon 420-743, Korea*

S. W. Han and K. H. Kim  
*Department of Physics, Gyeongsang National University, Chinju 660-701, Korea*

K. J. Kim, B. S. Kim, H. J. Song, and H. J. Shin  
*Pohang Accelerator Laboratory (PAL), POSTECH, Pohang 790-784, Korea*

J. H. Shim and B. I. Min  
*Department of Physics, POSTECH, Pohang 790-784, Korea*  
(Dated: February 2, 2008)

Electronic structures of  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  have been investigated using photoemission spectroscopy (PES) and x-ray absorption spectroscopy (XAS). The Co 3d states are found to lie near the top of the O 2p valence band, with a peak around  $\sim 3$  eV binding energy. The Co 2p XAS spectrum provides evidence that the Co ions in  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  are in the divalent  $\text{Co}^{2+}$  ( $d^7$ ) states under the tetrahedral symmetry. Our finding indicates that the properly substituted Co ions for Zn sites will not produce the diluted ferromagnetic semiconductor property.

PACS numbers:

Diluted magnetic semiconductors (DMSs) are considered as good candidates for spintronics materials because of the possibility of incorporating the spin degree of freedom in traditional semiconductors<sup>1,2</sup>. Motivated by the recent theoretical calculations by Dietl *et al.*<sup>3</sup> which predicted room-temperature ferromagnetism in Mn-doped ZnO,  $\text{Zn}_{1-x}\text{T}_x\text{O}$  systems (T = 3d transition-metal atom) have been investigated extensively. Indeed there were reports that  $\text{Zn}_{1-x}\text{Mn}_x\text{O}$  epitaxial thin films exhibited ferromagnetic properties<sup>4,5</sup> and that  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  films showed ferromagnetism with the Curie temperature  $T_C \sim 300$  K<sup>6</sup>. However, the reproducibility is somewhat questionable, and there are contradicting reports on Co-doped ZnO<sup>6,7,8</sup>. Technologically ZnO-based DMSs of  $\text{Zn}_{1-x}\text{T}_x\text{O}$  attract much attention due to the cheapness and abundance of ZnO, and the easy solubility of T atoms in ZnO up to several ten %<sup>4,9</sup>. In addition, since ZnO has a wide band gap energy of  $\sim 3.4$  eV, ZnO-based DMSs would be useful for short wavelength magneto-optical applications.

In order to understand the magnetic interaction in  $\text{Zn}_{1-x}\text{T}_x\text{O}$ , it is essential to understand the electronic structure of the doped 3d T impurities in  $\text{Zn}_{1-x}\text{T}_x\text{O}$ . Photoemission spectroscopy (PES) is one of the powerful experimental methods for providing direct information on the electronic structures of solids. To our knowledge, only a few PES studies have been reported on  $\text{Zn}_{1-x}\text{T}_x\text{O}$ : the PES study on  $\text{Zn}_{1-x}\text{Mn}_x\text{O}$ <sup>10</sup> and the Co 2p core-level PES spectra for  $\text{Zn}_{1-x}\text{Co}_x\text{O}$ <sup>8</sup>.

In this study we have investigated the electronic structure of homogeneous bulk samples of  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  using PES and x-ray absorption spectroscopy (XAS). Differently from previously reported film samples<sup>6</sup>, magnetic properties of our bulk  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples revealed that

the Co-Co magnetic interaction is dominated by the antiferromagnetic coupling<sup>11</sup>. Magnetic susceptibility at high temperature exhibits a typical Curie-Weiss behavior with negative  $T_C$  and the magnetization of Co ion is reduced with increasing the Co ion concentration reflecting an increase in average antiferromagnetic interaction between Co ions. Hence the present bulk sample is not a diluted ferromagnetic semiconductor.

Polycrystalline  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples ( $x = 0, 0.1$ ) were synthesized using the standard solid-state reaction method.  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples were obtained by sintering a mixed powder of  $(1-x)\text{ZnO} + x\text{CoO}$  at  $T \simeq 1400^\circ\text{C}$  for 2 hours followed by the furnace cooling in air. The x-ray diffraction (XRD) analysis showed that all the samples have the single phase of the Wurtzite structure with no impurity phase. Valence-band PES, XAS and Co 2p  $\rightarrow$  3d resonant photoemission spectroscopy (RPES) measurements were performed at the 2B1 and 8A1 beamlines of the PAL. Samples were cleaned *in situ* by repeated scraping with a diamond file and the data were obtained at room temperature with the pressure better than  $4 \times 10^{-10}$  Torr. The Fermi level  $E_F$ <sup>12</sup> and the overall instrumental resolution (FWHM) of the system were determined from the valence-band spectrum of a sputtered Au foil in electrical contact with a sample. The FWHM was about 0.1–0.6 eV between a photon energy  $h\nu \sim 30$  eV and  $h\nu \approx 600$  eV. All the spectra were normalized to the mesh current. The XAS spectra were obtained by employing the total electron yield method. The experimental energy resolution for the XAS data was set to  $\sim 0.2$  eV at the Co 2p absorption threshold ( $h\nu \approx 700$  eV). Core-level spectra and the valence-band spectrum with  $h\nu = 1486.6$  eV were obtained by using the monochromatized Al  $K\alpha$  radiation with a FWHM of  $\sim 0.6$  eV.

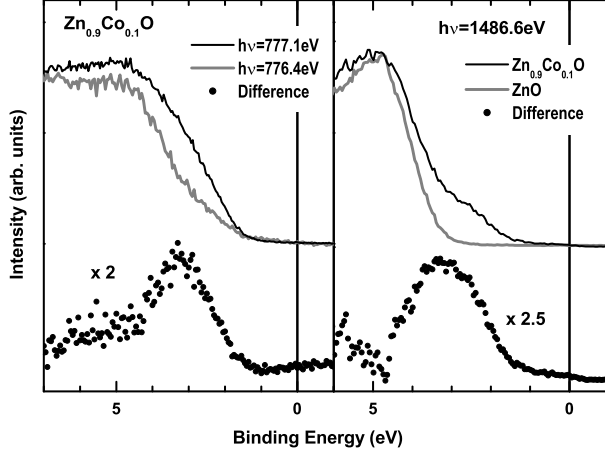


FIG. 1: Left: Comparison of the Co  $2p_{3/2} \rightarrow 3d$  on-resonance spectrum ( $h\nu \approx 777.1$  eV) and the off-resonance spectrum ( $h\nu \approx 776.4$  eV) for  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ , scaled at  $\sim 7$  eV BE. Right: Comparison of the valence-band spectrum of  $\text{ZnO}$  and that of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$ , obtained with  $h\nu = 1486.6$  eV. For both cases, the difference curves are shown at the bottom.

We have measured the valence-band PES spectra of  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  ( $x = 0, 0.1$ ) over a wide several photon energy range  $25 \text{ eV} \leq h\nu \leq 1486.6 \text{ eV}$ , which includes the Co  $2p \rightarrow 3d$  RPES energies (see Fig. 2). Our valence-band PES spectrum of  $\text{ZnO}$  agrees with the existing data in the literature<sup>13</sup>. Valence-band spectra for  $\text{ZnO}$  and  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  were rather similar, showing two large structures, one sharp peak around 11 eV binding energy (BE), and the other broad band between  $\sim 3$  eV and  $\sim 7$  eV BE. The former and latter peaks are assigned as the Zn  $3d$  and O  $2p$  emissions, respectively. They also reveal negligible emission near  $E_F$ , reflecting that both  $\text{ZnO}$  and  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  are insulating.

The left panel of Fig. 1 compares the on-resonance ( $h\nu \approx 777.1$  eV) and off-resonance ( $h\nu \approx 776.4$  eV) spectra for  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  in the Co  $2p_{3/2} \rightarrow 3d$  RPES, which are scaled to each other at  $\sim 7$  eV BE. The difference between on-resonance and off-resonance can be considered as representing the Co  $3d$  partial spectral weight distribution (PSW)<sup>14</sup>. The right panel of Fig. 1 compares the valence-band spectrum of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  to that of  $\text{ZnO}$ , obtained with  $h\nu = 1486.6$  eV. The differences between  $x = 0$  and  $x = 0.1$  also reflect the effect of the Co  $3d$  states. In both cases the differences are shown at the bottom, which are very similar to each other, showing a peak around  $\sim 3$  eV BE and negligible emission near  $E_F$ <sup>15</sup>. These results provide evidence that the Co  $3d$  states in  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  are located near the top of the O  $2p$  valence band.

The extracted Co  $3d$  PSW reveals almost no emission between  $E_F$  and 2 eV BE. This feature does not agree with the calculated Co  $3d$  PDOS (partial density of states), obtained from the LSDA (local spin-density

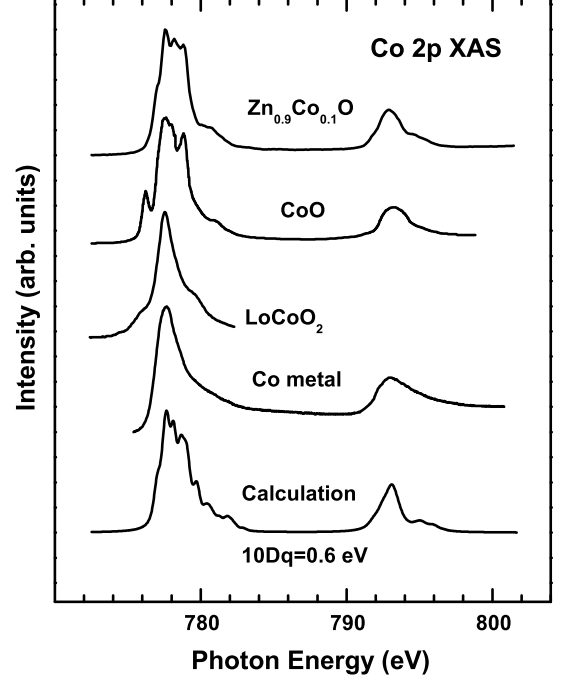


FIG. 2: The Co  $2p$  XAS spectrum of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  in comparison to those of  $\text{CoO}$  ( $\text{Co}^{2+}$ ) [Ref.<sup>18</sup>],  $\text{LiCoO}_2$  ( $\text{Co}^{3+}$ ) [Ref.<sup>19</sup>], and Co metal [Ref.<sup>18</sup>]. The data for  $\text{CoO}$ ,  $\text{LiCoO}_2$ , and Co metal were shifted by  $+0.1$  eV,  $-3.64$  eV and  $-0.1$  eV, respectively. The calculated Co  $2p$  XAS spectrum for low-spin  $\text{Co}^{2+}$  under the  $T_d$  symmetry is presented at the bottom.

approximation) band structure calculation<sup>16</sup>. The calculated Co  $3d$  PDOS for  $\text{Zn}_{0.75}\text{Co}_{0.25}\text{O}$  shows a sharp  $e_g^2 \downarrow$  peak near  $E_F$ . To resolve this discrepancy, more elaborate calculations such as LSDA+ $U$  incorporating the Coulomb correlation  $U$  between Co  $3d$  electrons will be required because it is well known that the LSDA calculation does not properly describe the electronic structures of insulators with strongly correlated electrons<sup>17</sup>.

Figure 2 compares the Co  $2p$  XAS spectrum of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  with those of reference Co oxides, having the formal Co valences of  $2+$  ( $\text{CoO}$ , Ref.<sup>18</sup>) and  $3+$  ( $\text{LiCoO}_2$ , Ref.<sup>19</sup>), and that of Co metal (Ref.<sup>18</sup>). Note that Co ions both in  $\text{CoO}$  and  $\text{LiCoO}_2$  are located at the octahedron ( $O_h$ ) centers. The peak positions and the line shape of the T  $2p$  XAS spectrum depend on the local electronic structure of the T ion, providing the information about the valence state and the ground state symmetry of the T ion<sup>20,21,22</sup>. The Co  $2p_{3/2}$  and  $2p_{1/2}$  spectral parts are clearly separated by the large  $2p$  core-hole spin-orbit interaction, and the core-hole lifetime broadening is small, resulting in the sharp multiplet structures. The Co  $2p$  XAS spectrum of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  looks similar to that of  $\text{CoO}$  except for the absence of the low- $h\nu$  shoulder ( $h\nu \sim 776$  eV), but quite different from those of  $\text{LiCoO}_2$  and Co metal. This observation indicates that Co ions in

$\text{Zn}_{1-x}\text{Co}_x\text{O}$  might be in the divalent  $\text{Co}^{2+}$  valence states, but not in the trivalent  $\text{Co}^{3+}$  valence states, and that the formation of the Co metal cluster in our  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples can be ruled out.

In order to estimate the valence state of Co ions in the ground states, we have analyzed the Co 2*p* XAS spectrum of  $\text{Zn}_{0.9}\text{Co}_{0.1}\text{O}$  within the cluster model where the effects of the multiplet interaction, the crystal field, and the hybridization with the O *p* ligands are included<sup>21</sup>. The calculated XAS spectrum is shown at the bottom of Fig. 2. We have found that including only one configuration, corresponding to  $\text{Co}^{2+}$  ( $d^7$ ), and the tetrahedral ( $T_d$ ) crystal field energy of  $10Dq = 0.6$  eV yields a good fit for the measured 2*p* XAS spectrum<sup>23</sup>. The analysis shows that it is not necessary to include the charge-transfer configuration,  $d^{n+1}\underline{L}^1$  ( $\underline{L}$ : a ligand hole), indicating that the hybridization between Co 3*d* and O *p* orbitals is small, in contrast to Mn-doped ZnO case<sup>10</sup>. We have checked that small changes in the parameters do not affect the overall spectral shape including the prominent peak positions. Based on the calculated XAS spectrum, one can conclude that the doped-Co ions in  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  are divalent in the ground states, i.e.,  $\text{Co}^{2+}$  ( $S = 3$ ) under the  $T_d$  symmetry with a small crystal field energy<sup>24</sup>. Our finding

suggests that, in our samples, Co ions substitute properly for the Zn sites with  $\text{Co}^{2+}$  valence states. In view of no long range ferromagnetic order in our samples, the reported DMS properties in some Co-doped  $\text{ZnO}$ <sup>6,8</sup> are likely to be extrinsic, that is, to originate from Co cluster or other impurity phases.

In conclusion, the electronic structures of bulk  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples have been investigated by employing PES and XAS. According to the Co 2*p*  $\rightarrow$  3*d* RPES and the careful comparison between  $x = 0$  and  $x = 0.1$ , the Co 3*d* states in  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  are found to lie near the top of the O 2*p* valence band with a peak around  $\sim 3$  eV BE. The measured Co 2*p* XAS spectrum shows that the ground states of Co ions in  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  are the divalent  $\text{Co}^{2+}$  states under the  $T_d$  symmetry corresponding to the total spin of  $S = 3$  per Co ion. Our finding suggests that the properly substituted Co ions in Co-doped ZnO do not produce the DMS property with the long range ferromagnetic order.

Acknowledgments— This work was supported by the KRF (KRF-2002-070-C00038) and by the KOSEF through the CSCMR at SNU and the eSSC at POSTECH. The PAL is supported by the MOST and POSCO in Korea.

- 
- \* Author to whom all correspondence should be addressed: kangjs@catholic.ac.kr
- <sup>1</sup> J. K. Furdyna, J. Appl. Phys. **64**, R29 (1988).
  - <sup>2</sup> S. A. Wolf, D. D. Awschalom, R. A. Buhrman, J. M. Daughton, S. von Molnar, M. L. Roukes, A. Y. Chtchelkanova, and D. M. Treger, Science **294**, 1488 (2001).
  - <sup>3</sup> T. Dietl, H. Ohno, F. Matsukura, J. Cibert, and D. Fermand, Science **287**, 1019 (2000).
  - <sup>4</sup> T. Fukumura, Z. Jin, A. Ohtomo, H. Koinuma, M. Kawasaki, Appl. Phys. Lett. **75**, 3366 (1999).
  - <sup>5</sup> S. W. Jung, S.-J. An, G. C. Yi, C. U. Jung, S. I. Lee, and S. Cho, Appl. Phys. Lett. **80**, 4561 (2002).
  - <sup>6</sup> K. Ueda, H. Tabata, and T. Kawai, Appl. Phys. Lett. **79**, 988 (2001).
  - <sup>7</sup> J. H. Kim, H. Kim, D. Kim, Y. E. Ihm, and W. K. Choo, J. Appl. Phys. **92**, 6066 (2002).
  - <sup>8</sup> H. J. Lee, S. Y. Jeong, C. R. Cho, and C. H. Park, Appl. Phys. Lett. **81**, 4020 (2002).
  - <sup>9</sup> Z. Jin, M. Murakami, T. Fukumura, Y. Matsumoto, A. Ohtomo, M. Kawasaki, and H. Koinuma, J. Crystal Growth **214/215**, 55 (2000).
  - <sup>10</sup> T. Mizokawa, T. Nambu, A. Fujimori, T. Fukumura, and M. Kawasaki, Phys. Rev. B **65**, 085209 (2002).
  - <sup>11</sup> S. W. Yoon, S.-B. Cho, S. C. Wi, S. Yoon, B. J. Suh, H. K. Song, and Y. J. Shin, J. Appl. Phys. **93**, 7879 (2003).
  - <sup>12</sup> Since  $\text{Zn}_{1-x}\text{Co}_x\text{O}$  samples are insulating, there is some ambiguity in determining  $E_F$ . However, the charging did not distort the valence-band lineshape with time.
  - <sup>13</sup> M. Ruckh, D. Schmid, and H. W. Schock, J. Appl. Phys. **76**, 5945 (1994).
  - <sup>14</sup> J.-S. Kang, J. H. Kim, A. Sekiyama, S. Kasai, S. Suga, S. W. Han, K. H. Kim, T. Muro, Y. Saitoh, C. Hwang, C. G. Olson, B. J. Park, B. W. Lee, J. H. Shim, J. H. Park, and

- B. I. Min Phys. Rev. B **66**, 113105 (2002).
- <sup>15</sup> When the difference is obtained with the on-resonance and off-resonance spectra being scaled at the Zn 3*d* peak, we get another broad feature between  $\sim 4$  eV and  $\sim 8$  eV BE. This feature is ascribed to the Co 3*d*-O 2*p* hybridized states. Here we focus on the resonating feature which has rather pure Co 3*d* electron character.
- <sup>16</sup> K. Sato and H. K. Yoshida, Semicond. Sci. Technol. **17**, 367 (2002).
- <sup>17</sup> J. H. Park, S. K. Kwon, and B. I. Min, Physica B **281-282**, 703 (2000).
- <sup>18</sup> T. J. Regan, H. Ohldag, C. Stamm, F. Nolting, J. Lüning, J. Stöhr, and R. L. White, Phys. Rev. B **64**, 214422 (2001).
- <sup>19</sup> J. van Elp, J. L. Wieland, H. Eskes, P. Kuiper, G. A. Sawatzky, F. M. F. de Groot, and T. S. Turner, Phys. Rev. B **44**, 6090 (1991).
- <sup>20</sup> F. M. F. de Groot, J. C. Fuggle, B. T. Thole, and G. A. Sawatzky, Phys. Rev. B **42**, 5459 (1990).
- <sup>21</sup> G. van der Laan and I. W. Kirkman, J. Phys.: Condens. Matter **4**, 4189 (1992).
- <sup>22</sup> J.-Y. Kim, J.-H. Park, B.-G. Park, H.-J. Noh, S.-J. Oh, J. S. Yang, D.-H. Kim, S. D. bu, T.-W. Noh, H.-J. Lin, H.-H. Hsieh, and C. T. Chen, Phys. Rev. Lett. **90**, 017401 (2003).
- <sup>23</sup> The fitting parameters are scaled by 80% of the atomic Slater integrals ( $F(dd)$ ,  $F(pd)$ , and  $G(pd)$ ).
- <sup>24</sup> In the  $T_d$  symmetry for Co ions, one cannot distinguish between the low-spin (LS) and high-spin (HS) divalent  $\text{Co}^{2+}$  states because the  $e_g$  states are located below the  $t_{2g}$  states. This results in the same total spin  $S = 3$  for both the small (the so-called LS state) and high (the so-called HS state) values of  $10Dq$ .